

<b>Datasheet:</b>  <b>EN CuFe2P / CW107C</b> <b>Low alloyed Copper</b> <b>Tubes</b>  <b>Alumeco ApS</b> 21-03-2025		<b>Internal alloy name:</b> CW107C <b>Metal:</b> Copper  <b>Chemical Symbol:</b> CuFe2P  <b>EN:</b> EN CuFe2P <b>UNS:</b> C19400 <b>SS:</b> - <b>GB:</b> TFe2.5 <b>JIS:</b> -  <b>Also known as:</b> - <b>Alloy type:</b> Electrical conducting				
<b>Main usage:</b> <ul style="list-style-type: none"> <li>Automotive</li> <li>Cables and wires</li> <li>Clamps, connectors and fasteners</li> <li>Electrical installations</li> <li>Electronic products</li> <li>Lightning rods and grounding</li> </ul>		<b>Important norms and literature:</b>  <b>General Standards</b> EN 12449:2023: Copper and copper alloys – Seamless, round tubes for general purposes  <b>Geometric Tolerance:</b> EN 12449:2023: Copper and copper alloys – Seamless, round tubes for general purposes				
<b>Main properties:</b> <ul style="list-style-type: none"> <li>High thermal and electrical conductivity</li> <li>Excellent forming properties</li> </ul>						
<b>Chemical composition in %: EN 12449:2023</b>						
<b>Cu</b>	<b>Fe</b>	<b>Pb</b>	<b>Zn</b>	<b>P</b>	<b>Other elements</b>	
					<b>Each</b>	<b>Together</b>
Rest	2,1 – 2,6	Max. 0,03	0,05 – 0,2	0,015 – 0,15	-	Max. 0,2
<b>Mechanical properties: EN 12449:2023</b>						
Material Condition	Wall Thickness <i>t</i>	Tensile Strength <i>R<sub>m</sub></i>	0,2% proof strength <i>R<sub>p0,2</sub></i>	Elongation <i>A</i>	Hardness	
	Max. mm	Min. MPA	MPa	Min. %	HV	HBW
M	20	-	-	-	165 – 215	160 – 210
R300	10	300	Max. 250	25	-	-
H085	10	-	-	-	85 – 115	80 – 110
R370	5	370	Min. 250	15	-	-
H110	5	-	-	-	110 – 140	105 – 135
R420	5	420	Min. 320	5	-	-
H135	5	-	-	-	Min. 135	Min. 130
* Information values only;						
<b>Physical properties:</b>						
Density	Solidification range	Electrical conductivity	Thermal conductivity (20 °C)	Thermal expansion (20 - 300 °C)	Annealing temperature	E – modulus (20 °C)
g/cm <sup>3</sup>	°C	%IACS	W/m K	µm m <sup>-1</sup> K <sup>-1</sup>	°C	N / mm <sup>2</sup>
8,78	1084	64,7	262	17	-	123.000
<b>Properties and information's (3 Excellent; 2 Good; 1 Poor/not recommendable)<sup>1</sup></b>						
<b>Machinability (Zerspanbarkeitsindex): 20*</b> <small>*(CuZn39Pb3 = 100)</small>		<b>Joining Methods:</b> Soldering: 3 Brazing: 2 Oxy-acetylene welding: 1 Gas-shielded arc welding: 1 TIG welding: 1 MIG welding: 1 Spot/seam welding: 1 Butt welding: 2 Gluing/adhesion: 2		<b>Surface Treatment:</b> Polishing: Mechanical: 2 Electrolytic/chemical: 3  <u>Galvanizing:</u> 3  <u>Hot Dipping:</u> 3		
<b>Forming Methods:</b> Hot Formability: 2 Cold Formability: 3						
<b>Corrosion resistance:</b> Atmosphere: 2 Waters and alkaline: 2 Acids, Ammonia, Seawater: 1						
<small><sup>1</sup>Information extracted from Kupferverband;</small>						

## Tolerances for Tubes of CW107C

Dimensions: EN 12449:1999* Tolerances on diameter		
Nominal diameter $d$ (mm)	Tolerances on nominal diameter (mm)	
	Applicable to mean diameter	Applicable to any diameter including deviation from circular form for straight lengths
$3 \leq d \leq 10$	$\pm 0,06$	$\pm 0,12$
$10 < d \leq 20$	$\pm 0,08$	$\pm 0,16$
$20 \leq d \leq 30$	$\pm 0,12$	$\pm 0,24$
$30 \leq d \leq 50$	$\pm 0,15$	$\pm 0,30$
$50 \leq d \leq 100$	$\pm 0,20$	$\pm 0,50$
$100 \leq d \leq 200$	$\pm 0,50$	$\pm 1,00$
$200 \leq d \leq 300$	$\pm 0,75$	$\pm 1,50$
$300 \leq d \leq 450$	$\pm 1,00$	$\pm 2,00$

\* Values are referred from Table 16 of EN 12449:1999

Dimensions: EN 12449:1999* Tolerances on wall thickness					
Nominal outside diameter $D$ (mm)	Tolerances on nominal wall thickness $t$ (mm)				
	%				
	$0,3 \leq t \leq 1$	$1 < t \leq 3$	$3 < t \leq 6$	$6 < t \leq 10$	$10 < t$
$3 \leq D \leq 40$	$\pm 15$	$\pm 13$	$\pm 11$	$\pm 10$	-
$40 < D \leq 120$	$\pm 15$	$\pm 13$	$\pm 12$	$\pm 11$	$\pm 10$
$120 \leq D \leq 250$	-	$\pm 13$	$\pm 13$	$\pm 12$	$\pm 11$
$250 \leq D \leq 450$	-	-	$\pm 15$	$\pm 15$	$\pm 15$

\* Values are referred from Table 17 of EN 12449:1999

Dimensions: EN 12449:1999* Tolerances on fixed lengths, tubes in straight lengths				
Nominal outside diameter $D$ (mm)	Tolerance on fixed length $l$ (mm)			
	$l \leq 250$	$250 < l \leq 1000$	$1000 < l \leq 4000$	$4000 < l$
$3 \leq D \leq 25$	+1 0	+3 0	+5 0	By agreement
$25 < D \leq 100$	+2 0	+5 0	+7 0	
$100 < D \leq 450$	+3 0	+5 0	+10 0	

\* Values are referred from Table 18 of EN 12449:1999

Dimensions: EN 12449:1999* Tolerances on fixed lengths, tube in coils (not level wound)	
Specified length $L$ (m)	Tolerance %
$L \leq 50$	+2 0
$50 < L \leq 100$	+3 0
$100 < L$	+5 0

\* Values are referred from Table 19 of EN 12449:1999

Dimensions: EN 12449:1999* Tolerances on diameter including deviation from circular form, tube in coils		
Nominal outside diameter $D$ (mm)	Tolerances on nominal diameter including deviation from circular form	Applicable for coil inside diameter min.
$3 \leq D \leq 6$	$\pm 0,30$	400
$6 < D \leq 10$	$\pm 0,50$	600
$10 \leq D \leq 20$	$\pm 0,70$	800
$20 \leq D \leq 30$	$\pm 0,90$	1000

\* Values are referred from Table 20 of EN 12449:1999

**Dimensions: EN 12449:1999\***  
**Tolerances on straightness**

Ratio of	Depth of arc (see Figure 1)	
	$h_1$ in any length $l_1$ of 1000 mm max.	$h_2$ in any length $l_2$ of 400 mm max.
$r \leq 5$	2	0,8
$5 < r \leq 10$	3	1,2
$10 < r \leq 20$	4	1,6
$20 < r \leq 40$	5	2,0
$40 < r$	6	2,5

\* Values are referred from Table 21 of EN 12449:1999

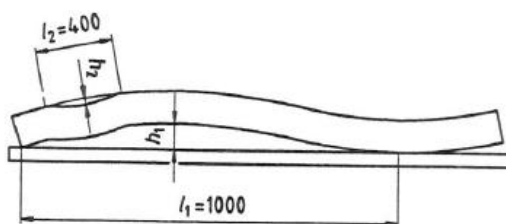


Figure 1 - Measurement of straightness from EN 12449:1999

**Dimensions: EN 12449:1999\***  
**Sampling rate**

Mass per unit length kg/m	Size of inspection lot for one test sample kg
$\bar{\lambda}_m \leq 0,25$	$\leq 500$
$0,25 < \bar{\lambda}_m \leq 5$	$\leq 1000$
$5 < \bar{\lambda}_m$	$\leq 2500$

\* Values are referred from Table 22 of EN 12449:1999